

## Effect of a modified photo-fenton procedure on the oxidative degradation of 1-naphthol in aqueous solution

L. Mammeri\*, W. Remache, S. Belaidi, K. Benhamouda, T. Sehili

Laboratoire des Sciences et Technologies de l'Environnement, Département de Chimie,  
Université des Frères Mentouri Constantine, Algérie.

\*Corresponding author: mammeri.lamia@umc.edu.dz ; Tel.: +21331 81 88 67; Fax: +21331 81 88 67

### ARTICLE INFO

#### Article History:

Received : 02/12/2016

Accepted : 08/11/2017

#### Key Words:

1-Naphthol;  
Natural iron oxide;  
Oxalic acid;  
Dedegradation;  
Photo-Fenton-like;  
Hydroxyl radicals.

### ABSTRACT/RESUME

**Abstract:** The photocatalytic degradation of 1-naphthol (1-NP) using natural iron oxide (NIO) as a heterogeneous catalyst in the presence of oxalic acid was investigated under UV irradiation. The characterization of this catalyst revealed that NIO has a mixed elemental composition and consists mainly of iron oxide ( $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>). This powder contains hematite as iron source and its dissolution provides Fe<sup>3+</sup> cations for the photo-Fenton-like reaction in solution. The degradation rate was strongly influenced by oxygen, initial concentration of oxalic acid (C<sub>ox</sub>) and 1-NP. The optimal C<sub>ox</sub> was 1mM. The first-order kinetic constant for the degradation of 1-NP decreased with the increase in the initial concentration of 1-NP. Furthermore, the variation of pH and the concentration of Fe<sup>2+</sup> during the photoreaction were also strongly dependent on the C<sub>ox</sub>. The use of 1% of tertibutanol as a scavenger confirmed the intervention of hydroxyl radicals in the photodegradation of 1-NP. Since both oxalic acid and iron oxides are common constituents of natural waters, this investigation will give a new insight to understanding the 1-NP photodegradation in natural environment.

### I. Introduction

Water pollution by organic chemicals has been of great concern over decades [1]. 1-Naphthol, widely used as an industrial intermediate, is of a particular concern due to its acute toxicity and negative environmental impacts once released to the receiving water systems via industrial waste streams [2]. Various forms of advanced oxidation processes (AOPs) have emerged as important alternatives for efficient mineralization of organic pollutants. Fenton process has its own unique advantages as an oxidizing process because its reagents are inexpensive, environmentally benign and relatively easy to transport and handle. The Fenton system involves the generation of hydroxyl radicals (<sup>•</sup>OH) which can degrade most organic compounds to carbon dioxide and water due to their high oxidation potential (E<sup>0</sup> = +2.80 V)[3].

The photochemical process that occurs with Fe<sup>2+</sup>/H<sub>2</sub>O<sub>2</sub>/UV is called photo-Fenton and that with

Fe<sup>3+</sup>/H<sub>2</sub>O<sub>2</sub>/UV is called photo-Fenton-like. In Fenton systems, H<sub>2</sub>O<sub>2</sub> is added as the direct source of <sup>•</sup>OH [4,5]. However, H<sub>2</sub>O<sub>2</sub> is an acute reactive reagent and cannot stand in nature for a long time. This factor limits the application of Fenton and Fenton-like system in the remediation of organic pollutants in nature. In fact, iron oxides, oxalic acid and sunlight can form a photochemical system to give a photo-Fenton-like reaction without the addition of H<sub>2</sub>O<sub>2</sub>, and with much higher quantum efficiency than with Fe(OH)<sup>2+</sup> or iron oxides alone [6,7].

Iron oxides are a kind of natural minerals and geocatalysts, widely existing in the earth's crust and also suspending in aqueous streams, aerosol, clouds, and fogs as fine particles [8]. Major iron oxides including hematite ( $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>), maghemite ( $\gamma$ -Fe<sub>2</sub>O<sub>3</sub>), goethite ( $\alpha$ -FeOOH), and lepidocrocite ( $\gamma$ -FeOOH) show semiconductor properties with a narrow band gap of 2.0–2.3 eV and could be photoactive under solar irradiation [9]. On the other

hand, oxalic acid has strong chelating ability with multivalent cations and is mainly exuded by plants in natural environment [10]. Oxalic acid is also an intermediate in the catalytic oxidation of phenol [11–14], and coumaric acid as a by-product of oil manufacturing [15].

In a word, this Fenton-like oxidation process can directly utilize natural mater (iron oxides and oxalic acid) in combination with solar energy, to decompose organic pollutants economically. It is meaningful to investigate the photodegradation of organic pollutants in the iron oxide–oxalate complex system to better understand the transformation of organic pollutants in natural surface water. In fact, the photochemistry of Fe(III)-oxalate complexes in natural aquatic environment, fog, precipitation, tropospheric aerosols and soil solution has received considerable attention over the past three decades [16–21] because iron oxide–oxalate exhibit strong ligand-to-metal charge absorption bands in the near-UV and visible region. The aims of this study were to investigate the photochemical degradation of 1-NP induced by F(III)-oxalate system and examining several factors that controlled the kinetics of 1-NP degradation.

## II. Materials and methods

### II.1. Reagents

All solutions were prepared with ultra-pure water (Millipore) with a resistivity of 18.2 mΩ.cm. The chemicals used in this study were 1-naphthol (99%+ Acros Organics), Oxalic acid (99.5% Prolabo), 1.10 phenantroline (Fluka analytical), sodium acetate and sulphuric acid (Panreac), Methanol (Carlo Erba Reagenti). All the chemicals were of analytical grade.

NIO is essentially constituted of hematite, it was used without any treatment; it was only washed several times with distilled water and dried at 45°C.

### II.2. Irradiation procedure

The irradiation experiments were performed in a Pyrex cylindrical reactor with a double envelopewas placed in the centre of the cylindrical stainless steel container. The photoreactor was exposed to the radiation sources composed of one low pressure mercury UV lamps type Philips HPW 125, (UV-A,  $\lambda_{max} = 365$  nm). The solution was continuous magnetically stirred with a magnetic bar during irradiation to insure its homogeneity.

The reactor was first filled with the suspension containing NIO particles. The required volume of mixed solution of 1-NP and oxalic acid were then added. The mixture was rapidly fed. The samples withdrawn at different reaction times were filtered with cellulose acetate filters (0.45  $\mu$ m) to separate NIO particles. At different time intervals during the irradiation, samples were collected and analyzed by HPLC. 1-NP was monitored at 290 nm by HPLC

(shimadzu). The mobile phase was a mixture of Methanol/water (60/40 v/v) was operated at a flow-rate of 1 mL min<sup>-1</sup> using Supelco, C18 column (5  $\mu$ m, 250 mm×4.6 mm i.d.). The solution pH was measured by means of an HANNA Instruments 8521 pH-meter. The Fe(II) concentration was measured by using a complexometric method with 1,10 phenanthroline. The red-formed complex was dosed after 1 h by UV–VIS at 510 nm. The molar absorption coefficient at 510 nm  $\epsilon$  is equal to 11153.63 M<sup>-1</sup> cm<sup>-1</sup>.

## III. Results and discussion

### III.1. Catalyst properties

The natural iron oxide (NIO) used in this work comes from a mineral in North East of Algeria. The analysis show that the NIO is not pure and contains predominantly  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> as reported in our previous paper [22]. While its composition and crystal structure was confirmed by X-ray powder diffraction (XRD). The specific surface area measured by Brunauer–Emmett–Teller (BET) method of NIO was 79.02 m<sup>2</sup>.g<sup>-1</sup> and the total pore volume was 0.0893 cm<sup>3</sup>.g<sup>-1</sup>.









### III.2. The effect of oxalic acid concentration

The effect of initial oxalic acid concentration ( $C_{ox}$ ) on the 1-NP degradation by the photo-Fenton-like reaction with 1.5 g.L<sup>-1</sup> NIO is shown in figure 1. The first-order kinetic constant (k) for 1-NP degradation increased with increasing  $C_{ox}$  from 0 to 1.5 mM (table 1).

One of the specificities of the photo-Fenton-like reaction studied in this paper is the use of oxalate (oxalic acid) that allows the forming of a photoactive complex. The Fe (III)-oxalate complex was formed according to Eq. (1). Its photolysis under UV irradiation in acidic solution form  $[Fe^{II}(C_2O_4)_{(n-1)}]^{(4-2n)}$  and oxalate radical  $(C_2O_4)^{\bullet-}$  as indicated by Eq. (2). In the solution,  $[Fe^{III}(C_2O_4)_n]^{(3-2n)}$  could be also excited under illumination to form  $[Fe^{II}(C_2O_4)_{(n-1)}]^{(4-2n)}$  and oxalate radical  $(C_2O_4)^{\bullet-}$  as described by Eq. (3). The oxalate radical can be transformed to the carbon-centered radical  $(CO_2)^{\bullet-}$  as described by Eq. (4), from which the excited electron is transferred to the adsorbed oxygen forming superoxide ion  $(O_2^{\bullet-})$ , as described by Eq. (5). Fe<sup>3+</sup> reacts with O<sub>2</sub><sup>•-</sup> to form O<sub>2</sub> and Fe<sup>2+</sup> as described by Eq. (7) and Fe<sup>2+</sup> reacts with O<sub>2</sub><sup>•-</sup> and <sup>•</sup>OOH to form H<sub>2</sub>O<sub>2</sub> in acidic solution with Fe<sup>3+</sup> as described by Eq. (8). Hydroxyl radicals (<sup>•</sup>OH) and Fe<sup>3+</sup> can be generated by the reaction of Fe<sup>2+</sup> with H<sub>2</sub>O<sub>2</sub> as described by Eq. (9).

**Table 1.** The pseudo-first-order kinetic constant (*k*), correlation coefficient (*R*) and removal percentage for 1-NP photodégradation with different initials concentrations of oxalic acid.

$C_{ox}^0$ (mM)	pH	$k \times 10^{-3} \text{ min}^{-1}$	<i>R</i>	Removal percentage (%) after 2 h
0.0	4.60	7.53	0.9798	63.45
0.5	4.01	10.84	0.9353	75.35
1.0	3.00	53.26	0.9796	99.77
1.5	2.26	38.23	0.9968	98.80
5.0	2.35	12.48	0.9625	82.22

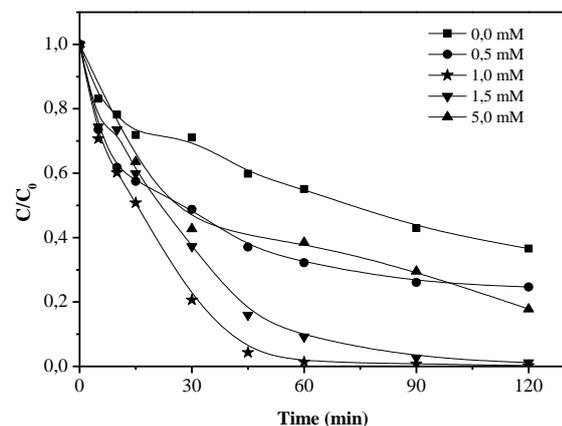


**Figure 1.** The effect of initial concentration of oxalic acid on the degradation of 1-NP ( $10^{-4}$  M) under UV irradiation using  $1.5 \text{ g.L}^{-1}$  NIO.

The increase of  $C_{ox}$  increases the production of the hydroxyl radicals. The negative effect observed at higher  $C_{ox}$  than 1 mM could be attributed to the competitive reactions between Fe(II) formed and the oxidant species generated in the ferrioxalate photolysis. The optimal  $C_{ox}$  in NIO-oxalate system

was 1mM. A higher  $C_{ox}$  would lead to lower pH at the beginning of reaction which was not favorable to photo-Fenton system [23].

### III.3. Fe(II) formation

The presence of Fe(II) resulting from the dissolution of  $\alpha\text{-Fe}_2\text{O}_3$  was checked out in the filtered aliquots by complexometry with ortho-phenantroline. Figure 2. showed the variation of Fe(II) concentration versus reaction time in the presence of different  $C_{ox}$  with  $1.5 \text{ g.L}^{-1}$  of NIO. During the photoreaction, NIO would be photo-dissolved. F(III)-oxalate complexes could generate Fe(II) species by the photo-reduction of dissolved Fe(III) species. The results indicated that generation of Fe(III)/Fe(II) under UV irradiation depended strongly on the  $C_{ox}$ . In the absence of oxalic acid, no dissolved Fe(III)/Fe(II) were found. On the other hand, higher  $C_{ox}$  led to the more Fe(II) concentration.

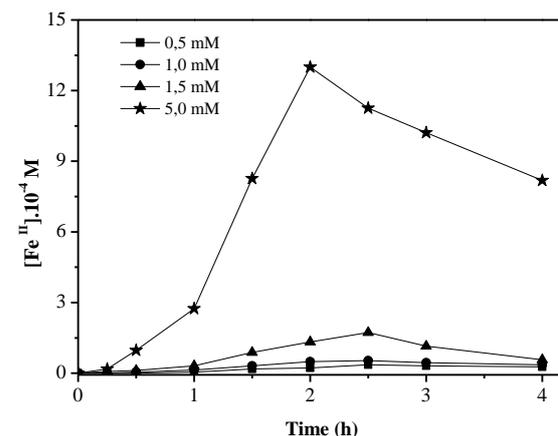


**Figure 2.** The concentration of the dissolved Fe(II) vs. reaction time with different initial concentration of oxalic acid by using  $1.5 \text{ g.L}^{-1}$  NIO under UV irradiation.

At the beginning of the photochemical process, the concentration of Fe(II) increased rapidly and attained the peak because  $\equiv\text{Fe}(\text{III})\text{-oxalate}$  can be easily photodissolved and reduced under irradiation

[24] and Fe(II) could be formed during this period as indicated by Eqs (3) and (7). In the late stage of the photochemical process, the formation of Fe(II) species decrease significantly with the decrease of oxalic acid which lead gradually to the increase of pH and Fe(III) precipitated as Fe(OH)<sub>3</sub>.


#### III.4. The variation of pH value

The pH value is an important factor that influences the photo-Fenton-like reaction. The variations of pH versus reaction time by using 1.5 g.L<sup>-1</sup> of NIO with different C<sub>ox</sub> are plotted in figure 3. It can be seen that the pH value increased gradually with the reaction time. The pH value increased significantly from 3,70 ; 3,00 ; 2,88 and 2,35 before photoreaction to 5,03 ; 5,15; 5,40 and 5,70 after 4 h photoreaction when the C<sub>ox</sub> were 0,5 mM, 1 mM, 1,5 mM and 5 mM respectively.

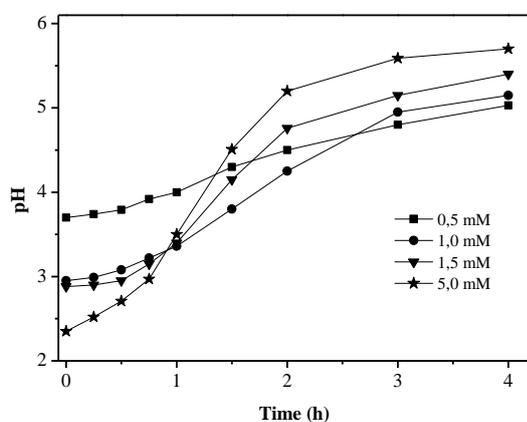

**Figure 3.** The variation of pH value during 1-NP (10<sup>-4</sup> M) degradation with different C<sub>ox</sub> by using 1.5 g.L<sup>-1</sup> of NIO under UV irradiation.

At the beginning, a higher C<sub>ox</sub> led to lower initial pH value. However, the pH in the solution increased much more slowly in the presence of a lower C<sub>ox</sub> than that of the higher one. The increase of pH value was mainly attributed to the dissolution of NIO and the formation of Fe(III)-oxalate complex. A higher C<sub>ox</sub> lead to more [≡Fe(C<sub>2</sub>O<sub>4</sub>)<sub>n</sub>]<sup>(2n-3)-</sup> to be formed. During the photochemical process, OH<sup>-</sup> would be generated in accompany with the generation of HO<sup>•</sup> as Eq. (10) [25,26]. More [≡Fe(C<sub>2</sub>O<sub>4</sub>)<sub>n</sub>]<sup>(2n-3)-</sup> in the system can generate more OH<sup>-</sup> so as to increase the pH value more in the solution in the later stage during the photochemical process.




#### III.5. The effect of initial 1-NP concentration

The effect of initial 1-NP concentrations on the rate of 1-NP degradation was performed by varying initial 1-NP concentrations from 0.5 × 10<sup>-4</sup> to 5.0 × 10<sup>-4</sup> M in the presence of 1.0 mM oxalic acid by using 1.5 g.L<sup>-1</sup> NIO under UV irradiation. A linear correlation was observed for 1-NP concentration and irradiation time (ln [C<sub>0</sub>/C] vs time). Hence degradation of 1-NP by the photo-Fenton-like system followed pseudo-first order kinetics.

$$\ln \frac{C_0}{C} = kt \quad (11)$$

Where *k* is the pseudo-first order rate constant. The experimental results obtained (figure. 4) show that the increase of initial 1-NP concentration from 0.5 × 10<sup>-4</sup> to 5.0 × 10<sup>-4</sup> M decreases the degradation rate constant from 63.50 × 10<sup>-3</sup> (R<sup>2</sup> = 0.9822) to 12.91 × 10<sup>-3</sup> min<sup>-1</sup> (R<sup>2</sup> = 0.9952), this is due to the competition between 1-NP and its reaction by-products for catalyst particles and such competition becomes more pronounced at higher concentrations.

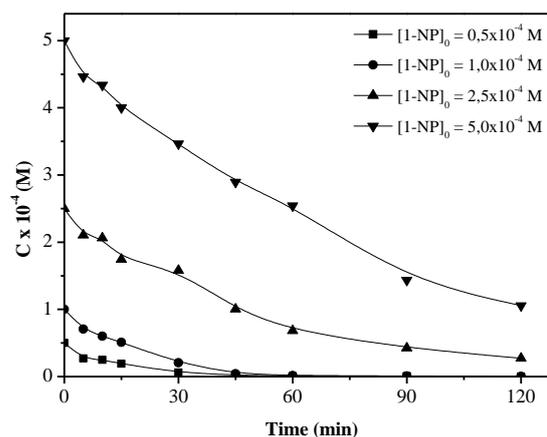

**Figure 4.** The effect of initial concentration of 1-NP on photo-Fenton-like degradation of 1-NP (initial conditions: 1 mM Maxalic acid, 1.5 g.L<sup>-1</sup> NIO) under UV irradiation.

#### IV. Conclusion

The heterogeneous iron oxide–oxalate complex system, as a photo-Fenton-like system, was set up in the presence of natural iron oxide and oxalate together. 1-NP could be effectively degraded in the system under UV irradiation. The present study has demonstrated that the 1-NP degradation followed the first-order kinetics. The experimental results indicated that the photocatalytic oxidation efficiency was enhanced with a decrease in 1-NP concentration and a limited increase in the oxalate dose. The optimal (C<sub>ox</sub>) was 1 mM. This factor have an impact on the concentration of Fe(II) formation and 1-NP disappearance. The good degradation of the organic contaminants is attributed to the generation of highly oxidative <sup>•</sup>OH radicals during

the photo-Fenton-like reaction. This work could help us to fully understand the photoreaction process concerning F(III)-oxalate complex for the degradation of pollutants in the aquatic environment under irradiation.

## V. References

1. W. Zhang, C. Hong, B. Pan, Z. Xu, Q. Zhang, L. Lv, Removal enhancement of 1-naphthol and 1-naphthylamine in single and binary aqueous phase by acid-basic interactions with polymer adsorbents, *Journal of Hazardous Materials*. 158 (2008) 293–299.
2. W. Zhang, C. Hong, J. Chen, B. Pan, Q. Zhang, P. Jiang, K. Jia, Sorption enhancement of 1-naphthol onto hydrophilic hyper-cross-linked polymer resin, *Journal of Hazardous Materials*. 163 (2009) 53–57.
3. G.V. Buxton, C.L. Greenstock, P.W. Helmen, A.B. Ross, Critical review of rate constants for reactions of hydrated electrons chemical kinetic data base for combustion chemistry. Part 3 : Propane, *Journal of Physical and chemical Reference Data*. 17 (1988) 513–886.
4. M. Pera-Titus, V. Garcia-Molina, M.A. Banos, J. Gimenez, S. Esplugas, Degradation of chlorophenols by means of advanced oxidation processes: a general review, *Applied Catalysis B: Environmental*. 47 (2004) 219–256
5. M.L. Kremer, Mechanism of the Fenton reaction. Evidence for a new intermediate, *Physical Chemistry Chemical Physics* 1(1999) 3595–3605.
6. C. Siffert, B. Sulzberger, Light induced dissolution of hematite in the presence of oxalate: A case study, *Langmuir*. 7 (1991) 1627–1634.
7. B.C. Faust, R.G. Zepp, Photochemistry of aqueous iron(III) polycarboxylate complexes: roles in the chemistry of atmospheric and surface waters, *Environmental Science and Technology* 27 (1993) 2517–2522.
8. U. Schwertmann, R.M. Cornell, *Iron Oxides in the Laboratory: Preparation and Characterization*, second ed., Wiley–VCH, 2000.
9. J.K. Leland, A.J. Bard, Photochemistry of colloidal semiconducting iron oxide polymorphs, *Journal of Physical Chemistry* 91 (1987) 5076–5083.
10. T. Kayashima, T. Katayama, Oxalic acid is available as a natural antioxidant in some systems, *Biochimica et Biophysica Acta*. 1573 (2002) 1 – 3.
11. R.V. Shende, V.V. Mahajani, Kinetics of wet air oxidation of glyoxalic acid and oxalic acid. *Ind. Eng. Chem. Res.* 33 (1994) 3125–3130.
12. A. Fortuny, C. Ferrer, C. Bengoa, J. Font, A. Fabregat, Catalytic removal of phenol from aqueous phase using oxygen or air as oxidant, *Catalysis Today*. 24 (1995) 79–83.
13. D. Duprez, F. Delanoe, J. Barbier Jr., P. Isnard, G. Blanchard, Catalytic oxidation of organic compounds in aqueous media, *Catalysis Today*. 29 (1996) 317–322
14. J.A. Zazo, J.A. Casas, A.F. Mohedano, M.A. Gilarranz, J.J. Rodriguez, Chemical pathway and kinetics of phenol oxidation by Fenton's reagent. *Environ. Sci. Technol.* 39 (2005) 9295–302.
15. D. Mantzavinos, R. Hellenbrand, A.G. Livingston, I.S. Metcalfe, Catalytic wet oxidation of p-coumaric acid: Partial oxidation intermediates, reaction pathways and catalyst leaching, *Applied Catalysis B: Environmental*. 7 (1996) 379–396.
16. Y. Zuo, J. Hoigne, Formation of hydrogen peroxide and depletion of oxalic acid in atmospheric water by photolysis of iron(III)-oxalato complexes, *Environ. Sci. Technol.* 26 (1992) 1014–1022.
17. R.G. Zepp, B.C. Faust, Hydroxyl radical formation in aqueous reactions (pH 3–8) of iron(II) with hydrogen peroxide: the photo-Fenton reaction, *Environ. Sci. Technol.* 26 (1992) 313–319.
18. V. Nadochenko, J. Kiwi, Photoinduced adduct formation between Orange II and  $[\text{Fe}^{3+}(\text{aq})]$  or  $\text{Fe}(\text{ox})_3^{3-}-\text{H}_2\text{O}_2$  Photocatalytic degradation and laser spectroscopy, *J. Chem. Soc. Faraday Trans.* 93 (1997) 2373–2378.
19. M.E. Balmer, B. Sulzberger, Atrazine Degradation in Irradiated Iron/Oxalate Systems: Effects of pH and Oxalate, *Environ. Sci. Technol.* 33 (1999) 2418–2424.
20. P. Mazellier, B. Sulzberger, Diuron Degradation in Irradiated, Heterogeneous Iron/Oxalate Systems: The Rate-Determining Step, *Environ. Sci. Technol.* 35 (2001) 3314–3320.
21. A. Bozzi, T. Yuranova, J. Mielczarski, A. Lopez, J. Kiwi, Abatement of oxalates catalyzed by Fe-silica structured surfaces via cyclic carboxylate intermediates in photo-Fenton reactions, *Chem. Commun.* 19 (2002) 2202.
22. L. Mammeri, T. Sehili, S. Belaidi, et K. Djebbar, Heterogeneous photodegradation of 1-naphthol with natural iron oxide in water: influence of oxalic acid, *Desalination Water Treat.* 54 (2015) 2324–2333.
23. L. Lunar, D. Sicilia, S. Rubio, D. Pérez-Bendito, et U. Nickel, Degradation of photographic developers by Fenton's reagent: condition optimization and kinetics for metol oxidation, *Water Res.* 34 (2000) 1791–1802.
24. C. Siffert et B. Sulzberger, Light-induced dissolution of hematite in the presence of oxalate. A case study, *Langmuir*. 7 (1991) 1627–1634.
25. K. A. Hislop et J. R. Bolton, The Photochemical Generation of Hydroxyl Radicals in the UV-vis/Ferrioxalate/ $\text{H}_2\text{O}_2$  System », *Environ. Sci. Technol.* 33 (1999) 3119–3126.
26. J. D. Rush et B. H. J. Bielski, Pulse radiolytic studies of the reaction of perhydroxyl/superoxide  $\text{O}_2^-$  with iron(II)/iron(III) ions. The reactivity of  $\text{HO}_2/\text{O}_2^-$  with ferric ions and its implication on the occurrence of the Haber-Weiss reaction, *J. Phys. Chem.* 89 (1985) 5062–5066.

**Please cite this Article as:**

Mammeri L., Remache W., Belaid S., Benhamouda K., Sehili T., *Effect of a modified photo-fenton procedure on the oxidative degradation of 1-naphthol in aqueous solution, Algerian J. Env. Sc. Technology, 3:3-A (2017) 05-10*